


NO-A103 043

LIQUID CRYSTALLINE POLYMERS CONTAINING
HETEROCYCLOALKANE MESOGENS 4 BIPHA. (U) CASE WESTERN
RESERVE UNIV CLEVELAND OH DEPT OF MACROMOLECULAR.
UNCLASSIFIED C S HSU ET AL. 1986 TR-9 N00014-86-K-0284 F/G 7/6

1/1

NL

ENT
9-81
B110

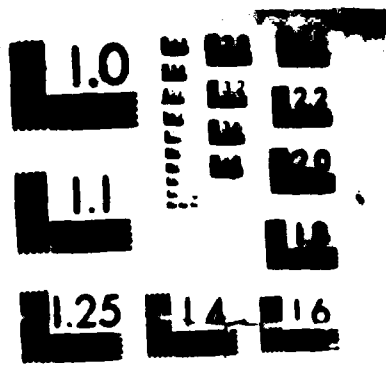

100% RESOLUTION TEST CHART

AD-A183 843

OFFICE OF NAVAL RESEARCH

Contract N00014-86-K-0284

R&T Code 413c024---01

Technical Report No. 9

DTIC
ELECTE
AUG 05 1987
S D

Liquid Crystalline Polymers Containing Heterocycloalkane Mesogens.

4. Biphasic Side-Chain Liquid Crystalline Polysiloxanes Containing
trans 5-(n-Undecanyl)-2-(4-Methoxyphenyl)-1,3- Dioxane and
trans 2-(n-Decanyl)-5-(4-Methoxyphenyl)-1,3-Dioxane Mesogens

By

Chain S. Hsu and Virgil Percec
Department of Macromolecular Science
Case Western Reserve University
Cleveland, OH 44106-2699

Reproduction in whole or in part is permitted for
any purpose of the United States Government.

This document has been approved for public release and sale;
its distribution is unlimited.

87 8 4 05 9

SECURITY CLASSIFICATION OF THIS PAGE

REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION Unclassified			1b. RESTRICTIVE MARKINGS	
2a. SECURITY CLASSIFICATION AUTHORITY			3. DISTRIBUTION / AVAILABILITY OF REPORT Available for publication Distribution unlimited	
2b. DECLASSIFICATION / DOWNGRADING SCHEDULE				
4. PERFORMING ORGANIZATION REPORT NUMBER(S) Technical Report No. 9			5. MONITORING ORGANIZATION REPORT NUMBER(S)	
6a. NAME OF PERFORMING ORGANIZATION Case Western Reserve University		6b. OFFICE SYMBOL (If applicable) 4B566	7a. NAME OF MONITORING ORGANIZATION ONR	
6c. ADDRESS (City, State, and ZIP Code) 2040 Adelbert Road Cleveland, OH 44106			7b. ADDRESS (City, State, and ZIP Code) Office of Naval Research Arlington, VA 22217	
8a. NAME OF FUNDING / SPONSORING ORGANIZATION ONR		8b. OFFICE SYMBOL (If applicable)	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER	
8c. ADDRESS (City, State, and ZIP Code) Office of Naval Research 800 N. Quincy Arlington, VA 22217			10. SOURCE OF FUNDING NUMBERS	
			PROGRAM ELEMENT NO. N00014-86	PROJECT NO. K-0284
11. TITLE (Include Security Classification) Liquid Crystalline Polymers Containing Heterocycloalkane Mesogens. 4. Biphaseic Side-Chain Liquid Crystalline Polysiloxanes Containing trans 5-(n-undecanyl)-2-(4-Methoxyphenyl)-1,3-Dioxane and				
12. PERSONAL AUTHOR(S) trans 2-(n-decanyl)-5-(4-Methoxyphenyl)-1,3-Dioxane Mesogens C. S. Hsu and V. Percec				
13a. TYPE OF REPORT Preprint		13b. TIME COVERED FROM TO	14. DATE OF REPORT (Year, Month, Day)	
15. PAGE COUNT				
16. SUPPLEMENTARY NOTATION				
17. COSATI CODES			18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number) Side-chain thermotropic liquid crystalline polymers	
FIELD	GROUP	SUB-GROUP		
19. ABSTRACT (Continue on reverse if necessary and identify by block number) See Attached.				
20. DISTRIBUTION / AVAILABILITY OF ABSTRACT <input checked="" type="checkbox"/> UNCLASSIFIED/UNLIMITED <input checked="" type="checkbox"/> SAME AS RPT. <input type="checkbox"/> DTIC USERS			21. ABSTRACT SECURITY CLASSIFICATION	
22a. NAME OF RESPONSIBLE INDIVIDUAL			22b. TELEPHONE (Include Area Code)	
			22c. OFFICE SYMBOL	


ABSTRACT

✓

The synthesis and characterization of side-chain liquid crystalline polysiloxanes and copolysiloxanes containing trans 5-(n-undecanyl)-2-(4-methoxyphenyl)-1,3-dioxane and respectively trans 2-(n-decanyl)-5-(4-methoxyphenyl)-1,3-dioxane side groups is presented. In most cases the resulting polymers exhibit two glass transition temperatures, i.e., one due to the independent motion of the main chain, and the other due to the independent but cooperative motion of the side chains.

↑

Accession For	
NTIS	CRA&I
DTIC	FAB
Unannounced	
Distribution	
By	
Distribution	
Availability Codes	
Dist	Avail and/or Special
A-1	



①

Liquid Crystalline Polymers Containing Heterocycloalkane Mesogens.

**4. Biphasic Side-Chain Liquid Crystalline Polysiloxanes
Containing trans 5-(n-Undecanyl)-2-(4-Methoxyphenyl)-1,3-
Dioxane and trans 2-(n-Decanyl)-5-(4-Methoxyphenyl)-1,3-
Dioxane Mesogens**

Chain S. Hsu and Virgil Percec*
Department of Macromolecular Science
Case Western Reserve University
Cleveland, Ohio 44106, USA

Summary

The synthesis and characterization of side-chain liquid crystalline polysiloxanes and copolysiloxanes containing trans 5-(n-undecanyl)-2-(4-methoxyphenyl)-1,3-dioxane and respectively trans 2-(n-decanyl)-5-(4-methoxyphenyl)-1,3-dioxane side groups is presented. In most cases the resulting polymers exhibit two glass transition temperatures, i.e., one due to the independent motion of the main chain, and the other due to the independent but cooperative motion of the side chains.

Introduction

The previous papers from this series reported on the synthesis and characterization of thermotropic side-chain liquid crystalline polymers (LCP) containing trans 2,5-disubstituted-1,3-dioxane mesogens attached to the polymer backbone through spacers containing eleven and respectively ten methylenic units (1, 2). Most of the previously synthesized LCP containing long spacers and calamitic mesogens underwent side-chain crystallization (3, 4). Since the trans 2,5-disubstituted-1,3-dioxane mesogens present a number of conformational isomers which are in a thermodynamic equilibrium, side-chain LCP containing long spacers and 1,3-dioxane based mesogens do not undergo side-chain crystallization. This particularity of the 2,5-disubstituted-1,3-dioxane mesogens let us design the first examples of thermotropic side-chain LCP exhibiting two glass transition temperatures, i.e., one due to the independent motion of the polymer backbone, and the other due to the independent but cooperative motion of the side-chains (5). These side-chain LCP are biphasic systems, and therefore can be regarded as polymers resembling the behavior of phase separated graft copolymers.

The goal of this paper is to present the synthesis and characterization of two new examples of biphasic side-chain LC polysiloxanes and copolysiloxanes containing side-chains whose mesogenic units are constitutional isomers, i.e., trans-5-(n-undecanyl)-2-(4-methoxyphenyl)-1,3-dioxane and trans 2-(n-decanyl)-5-(4-methoxyphenyl)-1,3-dioxane.









Experimental

A. Materials

Poly(methylhydrosiloxane)s ($\bar{M}_n = 4500 - 5000$ and $\bar{M}_n = 2270$) and poly [(30-35%) - methylhydro-(65-70%)-dimethylsiloxane] ($\bar{M}_n = 2000 - 2100$) were obtained from Petrarch Systems Inc., and were used as received. 4-Methoxybenzaldehyde and the other reagents (Aldrich) were used as received. Toluene used in the hydrosilation reaction was first refluxed over sodium and then distilled under argon.

B. Techniques

Experimental techniques used in the characterization of intermediary

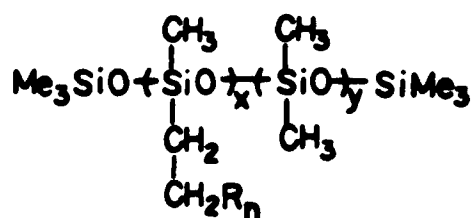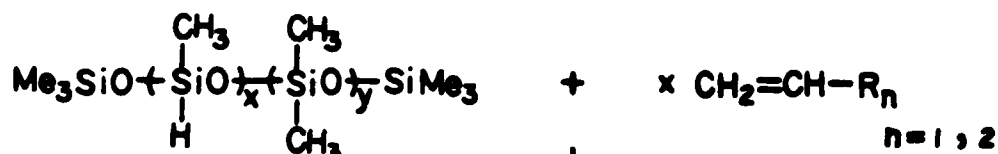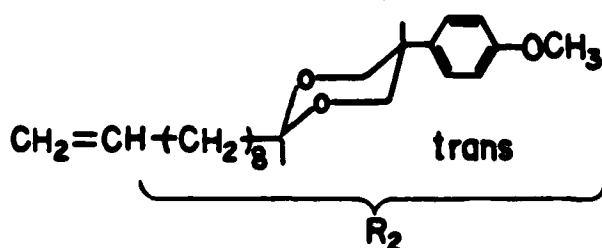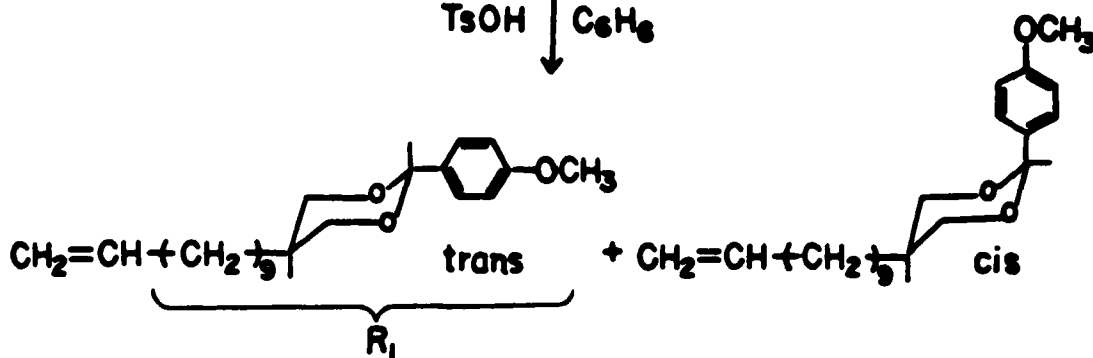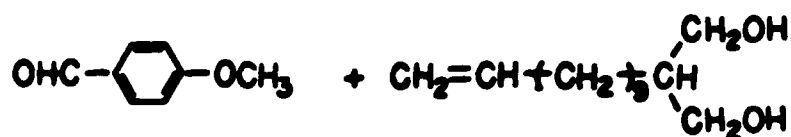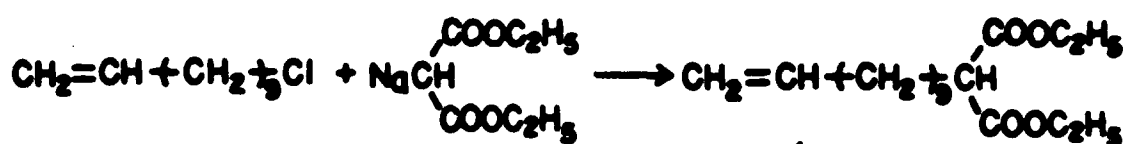

Scheme 1: Synthesis of LC Polysiloxanes and Copolysiloxanes Containing 2,5-Disubstituted-1,3-Dioxane Based Side-Groups

compounds and of polymers are identical to those previously reported (6).

C. Synthesis of Monomers and Polymers

2-(10-Decylenyl)-5-(4-methoxyphenyl)-1,3-dioxane was synthesized as previously reported (2). The syntheses of 5-(11-undecylenyl)-2-(4-methoxyphenyl)-1,3-dioxane and of the LC polysiloxanes and copolysiloxanes are outlined in Scheme 1.

Diethyl-2-(11-undecylenyl)malonate

Cleanly cut Na (3.45g, 0.15 mole) was added in portions to absolute ethanol (150 ml). After the sodium was completely dissolved, diethyl malonate (24g, 0.15 mole) was added to the reaction mixture and the solution was stirred for 1hr. 11-Chloro-1-undecene (28.3g, 0.15 mole) was then added to the reaction mixture. After 16 hrs of stirring at room temperature, the ethanol was evaporated on a rotavapor. The residue was dissolved in ethyl ether, washed several times with water, dried over anhydrous Na_2SO_4 , and ethyl ether was removed on a rotavapor. The product was distilled at 155-158°C/10-12 mm Hg, to yield 39g (83%). 200 MHz $^1\text{H-NMR}$ (CDCl_3 , TMS, δ , ppm): 1.13 to 2.08 (m, 24 H, $-(\text{CH}_2)_9-$ and $\text{CH}_3\text{CH}_2\text{O}-$), 3.30 (t, 1 H, $-\text{HC}(\text{CO})_2$), 4.20 (m, 4H, $-\text{CH}_2\text{O}$), 4.94 (m, 2 H, $\text{CH}_2=$), 5.80 (m, 1 H, $=\text{CH}-$).

2-(11-Undecylenyl)-1,3-propanediol

A solution of diethyl 2-(undecylenyl)malonate (39g, 0.125 mole) in 50ml of dried ethyl ether was added dropwise to a suspension of LiAlH_4 (4.75g, 0.125 mole) in 250ml of dried ethyl ether. After the addition was complete, the reaction mixture was stirred at 40°C for 20 hrs, cooled to room temperature, and excess LiAlH_4 was reacted with ethyl acetate. The resulting solution was treated with dilute hydrochloric acid and extracted with ethyl ether. The organic phase was washed with 2% aqueous solution of NaHCO_3 , water, and dried over anhydrous Na_2SO_4 . The crude product obtained after the solvent was evaporated was recrystallized from ethyl ether at 0°C to yield 27g (94%). m.p.=58-59°C. 200 MHz $^1\text{H-NMR}$ (CDCl_3 , TMS, δ , ppm): 1.06 to 2.16 (m, 18 H, $-(\text{CH}_2)_9-$), 3.30 to 3.81 (m, 5 H, $-\text{HC}(\text{CH}_2\text{O})_2$), 4.94 (m, 2 H, $\text{CH}_2=$), 5.80 (m, 1 H, $=\text{CH}-$).

Trans-5-(11-Undecylenyl)-2-(4-methoxyphenyl)-1,3-dioxane

2-(11-Undecylenyl)-1,3-propanediol (6g, 0.0262 mole), 4-methoxybenzaldehyde (3.6g, 0.0262 mole) and p-toluene sulfonic acid (250 mg) were dissolved in 250 ml of dried benzene. The reaction mixture was refluxed until 0.47 ml of water was collected on a Dean-Stark trap. After cooling to room temperature, the solution was washed with 2% aqueous solution of NaHCO_3 , water, dried over anhydrous Na_2SO_4 , and the solvent was evaporated on a rotavapor. The obtained solid was recrystallized several times from n-hexane at 0°C to yield 5.3g (58%). m.p.= 50°C. 200 MHz $^1\text{H-NMR}$ (CDCl_3 , TMS, δ , ppm): 1.11 to 2.16 (m, 19 H, $-(\text{CH}_2)_9-\text{CH}(\text{CH}_2-)_2$), 3.51 and 4.18 (m, 4 H, two $-\text{CH}_2\text{O}$), 3.79 (s, 3 H, $-\text{OCH}_3$), 4.94 (m, 2 H, $\text{CH}_2=$), 5.36 (s, 1 H, PhCH), 5.80 (m, 1 H, $=\text{CH}-$), 6.86 and 7.38 (2d, four aromatic protons).

Synthesis of Polymers and Copolymers

Polysiloxanes and copolysiloxanes were synthesized by hydrosilation of the corresponding olefins with poly(hydrogenmethylsiloxane)s or poly[(30-35%)-hydrogenmethyl-(65-70%)-dimethylsiloxane] using dicyclopentadienyl platinum (II) chloride as catalyst in toluene. A detailed description of a procedure for complete hydrosilation free of side reactions was previously reported (2).

Results and Discussion

Scheme 1 outlines the synthesis of trans 5-(11-undecylenyl)-2-(4-methoxyphenyl)-1,3-dioxane, shows the structure of trans 2-(10-decylenyl)-5-(4-methoxyphenyl)-1,3-dioxane, and presents the synthesis of the LC polysiloxanes and copolysiloxanes. The mesogenic unit and the aliphatic part of the side groups are denoted by R_1 and R_2 respectively. R_1 contains one more me-

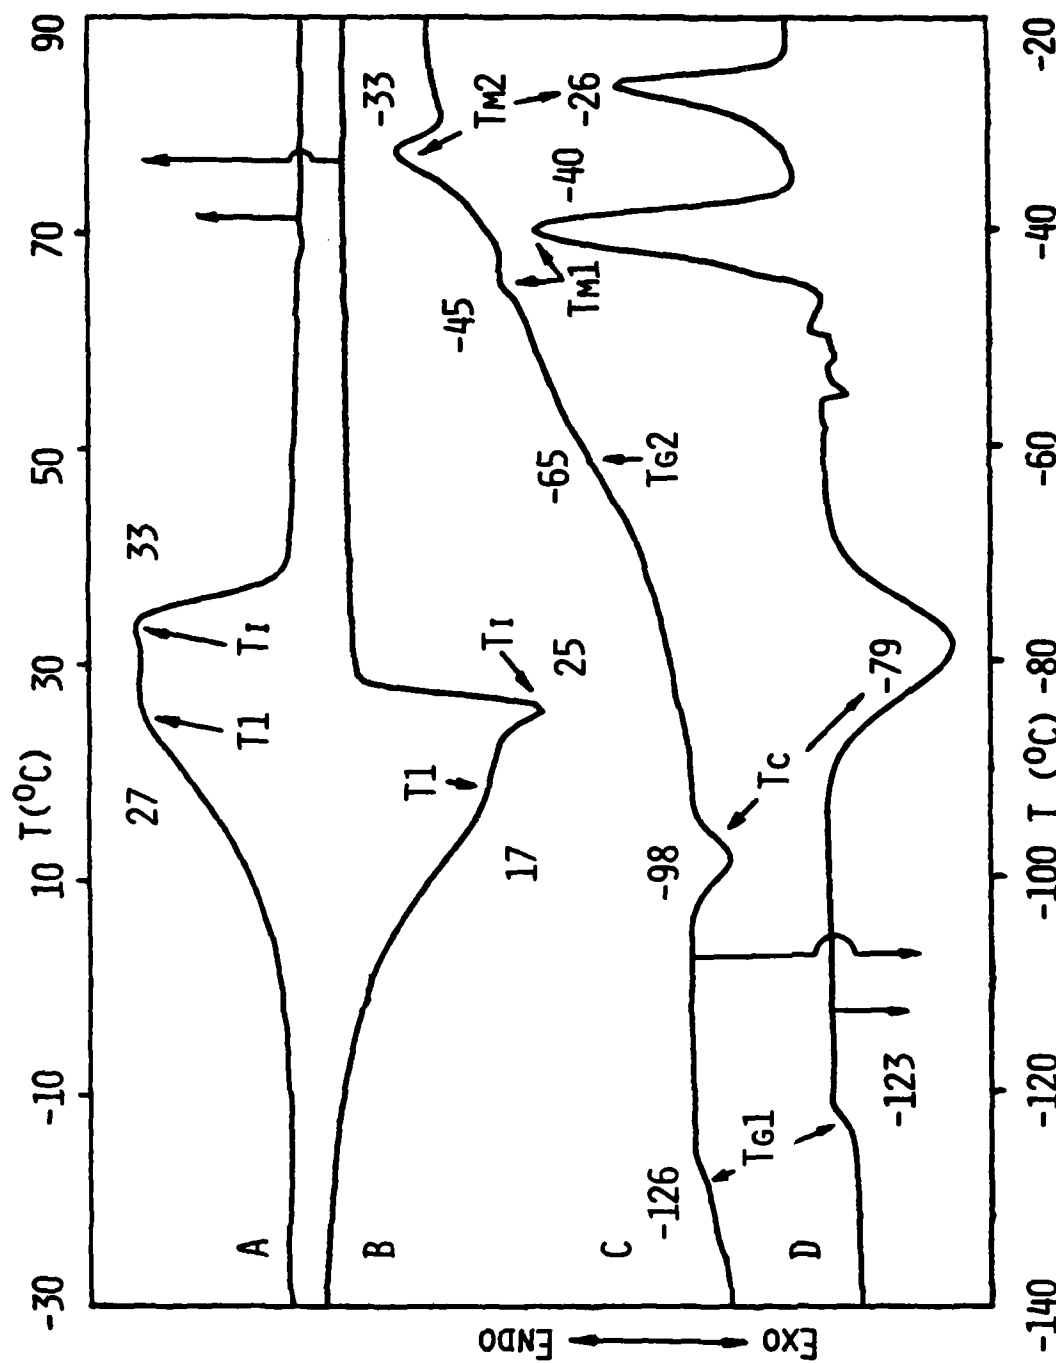


Figure 1: DSC thermograms (20 $^{\circ}\text{C}/\text{min}$) of: A) copolymer No. 4 from Table I, heating scan; B) cooling scan; C) heating scan; D) polydimethylsiloxane sample No. 5 from Table I, heating scan

TABLE 1: THERMAL TRANSITIONS OF POLYSILOXANES

POLYMER		THERMAL TRANSITIONS IN °C												
		HEATING										COOLING		
		No	RN	x*	y*	T _{G1}	T _C	T _{M1}	T _{M2}	T _{G2}	T _I			T _I
1	R1	80	0			-126	--	--	-35	-17	3	63	-5	57
2	R1	20	10			---	--	--	--	-46	16	52	9	46
3	R2	80	0			-126	--	--	-34	-7	84	93	77	84
4	R2	20	10			-127	-98	-45	-33	-65	27	33	17	25
5	--	0	80			-123	-79	-40	-27	--	--	--	--	--

* X AND Y ACCORDING TO SCHEME 1.

thylenic unit in the aliphatic spacer than R_2 . The mesogenic units of the two side groups are constitutional isomers.

Figure 1 presents typical differential scanning calorimetric traces of an LC copolysiloxane containing R_2 side groups (curves A and C heating scans; curve B, cooling scan) and of a polydimethylsiloxane (curve D). The polydimethylsiloxane sample exhibits the expected glass transition temperature (T_{g1}), followed by a crystallization exotherm (T_c), and two melting exotherms (T_{m1} , T_{m2}) (7). The LC copolysiloxane exhibits the glass transition temperature of the polysiloxane backbone (T_{g1}), followed by the crystallization of the polysiloxane backbone (T_c), the glass transition temperature of the side groups (T_{g2}), and the two meltings of the polysiloxane backbone (T_{m1} , T_{m2}). Since the glass transition temperature of the side groups, T_{g2} , is situated below the melting temperature of the polymer backbone, it demonstrates that the mobility of the LC domains is completely independent of the mobility of the backbone domains although they are interconnected.

The differential scanning calorimetric thermograms C and D from Figure 1 are quite similar, suggesting that at least the last methylenic unit of the spacer is part of the polymer backbone. The shifts observed for the thermal transitions of the LCP backbone versus those of the free polydimethylsiloxane backbone should be related to the weight ratio of the domains, domain size, and interfacial miscibility.

The high temperature range of the differential scanning calorimetric thermograms revealed both for homopolymers as well as for copolymers, two highly ordered mesophases (curves A and B in Figure 1), which have not been yet completely assigned. Preliminary X-ray diffraction data suggest higher order than smectic-B for the LC mesophase occurring at room temperature.

Table I summarizes the thermal transitions for all LCP. Only in the case of the copolymer No. 2 from this table we could not detect the thermal transitions due to the polysiloxane backbone. For the case of homopolymers, R_2 gives a more stable mesophase, while R_1 gives a more stable mesophase for copolymers. Since the lengths of the spacer are not the same, and because the LCP morphology is expected to affect also the mesomorphic behavior of the LC domains, it is not yet possible to comment further on these results. Nevertheless, it seems to be certain that the behavior of biphasic versus monophasic side-chain liquid crystalline polymers should be different.

Previously, comb-like polymers exhibiting two glass transition temperatures were seldom encountered in the literature (8, 9). Our previous results (5) together with the present data, suggest that with a proper selection of the polymer backbone and of the side groups, at list for high weight percent of side groups and long spacers, it should be quite easy to tailor a large variety of biphasic side chain LCP. It has to be mentioned that miscibility rules could play an important role in the design of such systems.

Acknowledgements

Financial support of this work by the Office of Naval Research is greatly acknowledged.

References

1. C. S. Hsu, J. M. Rodriguez-Parada and V. Percec, Makromol. Chem., in press
2. C. S. Hsu, J. M. Rodriguez-Parada and V. Percec, J. Polym. Sci. Part A: Polym. Chem., in press
3. H. Finkelmann and G. Rehage, Adv. Polym. Sci., 60/61, 99(1984)
4. V. P. Shibaev and N. A. Plate, Adv. Polym. Sci., 60/61, 173(1984)
5. C. S. Hsu and V. Percec, Makromol. Chem. Rapid Commun., submitted
6. J. M. Rodriguez-Parada and V. Percec, J. Polym. Sci. Part A: Polym. Chem., 24, 1363(1986)

7. S. J. Clarson, K. Dodgson and J. A. Semlien, *Polymer*, 26, 930(1985)
8. J. M. G. Cowie, Z. Hag and I. J. McEwen, *J. Polym. Sci., Polym. Lett. Ed.*, 17, 771(1979)
9. J. M. G. Cowie, Z. Hag, I. J. McEwen and J. Velickovic, *Polymer*, 22, 327(1981)

END

9-87

DTIC